

Trace Analysis of Ancient Gold Objects Using Radiochemical Neutron Activation

Agata Olariu*, Mioara Constantinescu, O. Constantinescu,
T. Badica, I. V. Popescu

National Institute of Physics and Nuclear Engineering
P.O.Box MG-6, 76900 Magurele, Bucharest, Romania

*e-mail: agata@tandem.ifa.ro

C. Besliu

Faculty of Physics, Bucharest

Doina Leahu

National History Museum, Bucharest

Abstract

Radiochemical neutron activation analysis has been applied to investigate the microelements in gold samples with archaeological importance. Chemical separation has allowed the determination of traces of Ir, Os, Sb, Zn, Co, Fe, Ni. Instrumental neutron activation analysis has been used for the determination of Cu.

Introduction

The chemical composition of any archaeological item can be used to develop characterisation and classification criteria ¹. In this work we have analysed a number of ancient gold objects from different gold hoards from the National History Museum, Bucharest, to answer some questions related to the composition of these objects. We present in Table 1 the list of gold samples of historical interest which have been studied in this work. Investigations of Emeleus² and Caley³ indicate that the non-destructive instrumental neutron activation analysis (INAA) is not suitable for the determination of various impurities in gold. Indeed, because of the spectroscopic interference effects or the low sensitivity of INAA, many impurities in gold matrix cannot be detected. Among the perturbative effects, the Ag with high concentrations in gold samples is a serious problem. The ancient gold samples contain relatively high concentrations of Ag > 1%, and after irradiation with thermal neutrons the gamma spectra of the samples, after the disintegration of gold, are dominated by the γ rays of the isotope ^{110m}Ag ($T_{1/2}=250$ d).

We have concluded that for the investigation of ancient gold samples by NAA, the chemical separation of Ag is required, and in this way the sensitivity of other minor elements in gold can be improved. A post-irradiation separation of the Ag from the gold sample, was chosen to avoid the contamination from the reagents used in the pre-irradiation separation procedure. RNAA has allowed the determination of Ir, Os, Sb, Zn, Co, Fe and Ni, in the ancient gold samples.

Experimental

RNAA. In order to determine some trace elements in ancient gold samples we have applied a RNAA technique. After neutron irradiation, the silver was precipitated as AgCl and centrifugated. The supernatant solution includes the traces of elements in the gold samples.

Preparation of samples: samples of $\approx 3\text{mg}$ were wrapped in pure Al foil. To diminish the self-shielding effects of neutron flux, the samples have been flattened⁴. A standard of gold of $0.105\text{ }\mu\text{g}$, 99.9% was used.

Irradiation: samples and the standard have been irradiated for 30 h at a neutron flux of $10^{13}\text{ neutrons/cm}^2\cdot\text{sec}$ in the VVR-S reactor of the NPNE, Bucharest-Magurele.

Preliminary measurements: in the first days after the irradiation, the gamma spectra are dominated by the photopeaks of ^{198}Au and after the disintegration of this, the spectra are dominated by ^{110m}Ag . This fact does not permit to determine other elements than Au and Ag in the gold samples. After $\approx 30 - 40$ d, the samples were counted to measure Au and Ag. The measurements have been performed with a Ge(Li) detector, 135 cm^3 and a Canberra 4096 channel analyser. The system gave a resolution of 2.4 keV at 1.33 MeV (^{60}Co). Preliminary spectral analysis has demonstrated the high sensitivity of the classical INAA procedure for Au and Ag.

Radiochemical separation procedure: by applying the chemical separation technique of Silver, several microimpurities, also present in gold could also be detected. The diagram from Fig. 1 indicates our radiochemical separation procedure of Ag from irradiated gold samples. The irradiated gold samples were dissolved in warm "aqua regia". After that, AgNO_3 as carrier and 4M HCl were added to this solution and silver was precipitated as AgCl. The precipitate was centrifuged and washed 3 times with 2.0 ml distilled H_2O till neutral pH. The aqueous phase from the washing of AgCl precipitate was added to the solution from the silver chloride precipitation.

In order to obtain a high degree of purification, the precipitation as AgCl has been repeated 3 times. Finally, the supernatant solution has been evaporated on a small plastic plate and counted. We determined the radiochemical yield for Au, by measuring the activity of Au in samples before, and after the chemical separation; the main value of the radiochemical yield for Au was in the range of 92%-95%. For the other elements we could not evaluate the radiochemical yield, because before the separation of Ag, these elements could not be seen, they were covered by the activity of Ag. It is to mention that the sample dissolution was difficult to access, therefore we have used the repeated dissolution with "aqua regia" and hot, concentrated, HNO₃ and HCl.

Measurements: after the Ag precipitation, the gold phase was measured. Gamma ray spectra were recorded for 20,000 s per sample. The concentrations of the microelements were determined by the measurement of the activity of the following photopeaks: Ir (316 keV), Os (646 keV), Sb (603 keV), Zn (1115.5 keV), Fe (1099 keV), Co (1332 keV), and Ni (811 keV). The Nickel concentration was determined by the 811 keV peak belonging to ⁵⁸Co isotope, arising from the ⁵⁸Ni(n,p)⁵⁸Co reaction. The instrumental errors of measurements are <20% for Os and <7% for Ir, Sb, Zn, Fe, Co and Ni.

Under our experimental conditions, the detection limits (i.e. the lowest concentration of the element under consideration that produces a peak under which the integrated area is equal to 3 times the square root of the background number of counts) are as follows: Ir: 2 - 10 ppb, Os: 1 - 4 ppm, Sb: 0.3 - 1 ppm, Zn: 1 - 6 ppm, Fe: 150 - 2000 ppm, Co: 0.05 - 0.10 ppm, Ni: 100 - 300 ppm.

INAA. Copper was not possible to be determined by the RNAA procedure and a special separate measurement was done: the samples of gold with Au and Cu pure 99.9% standards have been irradiated at a flux of 10^{12} neutrons/cm²·sec with a rabbit system from the same reactor, for 2 minutes. After a cooling time of 3...4 minutes, the samples were counted for 500 s, with a lead brick of a thickness of 2.5 cm interposed between the detector and the sample. The standard was counted after 30 min, in the same geometry as the sample. The radioactivity in the photopeak of 412 keV of ¹⁹⁸Au is attenuated ≈ 300 times and this fact has permitted to observe the photopeak of 1039 keV of ⁶⁶Cu ($T_{1/2}=5.1$ min), which is attenuated $\approx$ only 5 times by the lead brick. The instrumental errors of measurements are $<1\%$ for Au and Ag, and $<20\%$ for Cu. The limit of detection for Cu of this procedure was about 0.2%.

Results and Discussions

The experimental results concerning the elemental concentrations of ancient gold objects belonging to the National History Museum, Bucharest are presented in Table 2. The concentrations are expressed in % for the Ag and Cu contents, in ppb for Ir and in ppm for Os, Sb, Zn, Co, Fe and Ni. The instrumental errors of measurements are $<20\%$ for Os and also for Cu, and $<7\%$ for the other elements. The interpretation of the compositional scheme of gold items is complicated⁵ by the fact that the gold objects were frequently remelted during the history, but less for jewellery than for coins. Also the representativity of a sample of $\approx 1-3\text{mg}$, is questionable. Gold can be very inhomogeneous if it has not been melted.⁶ However based on several thousands of analyses of ancient gold objects using samples of about 1 mg, Hartmann was able to distinguish different types of gold compositions with geographically coherent distribution⁷.

For Au, Ag and Cu distribution in the gold samples, Fig. 2 represents Ag/Au and Cu/Au plots. The samples A1, A2 and A3 from Moigrad, Neolithic present close concentrations of Au, Ag and Cu with the samples from Moigrad 5th century hoard: A25, A26, A27 samples. The objects of the two hoards from Moigrad have the same discovery place and are dated by the historians very different, at a long distance (Table 1).

From the Fig. 2 it seems these gold hoards have the same major element composition. The sample of A24, the buckle has a different concentration of Cu ($C_{Cu}=6.89\%$) in comparison with the other items from Moigrad, with the concentration lying in the range $< 1\%$. The sample A24 is also distinguished with its higher concentrations of Ir $C_{Ir}=455$ ppb, Zn $C_{Zn}=3400$ ppm and Ni $C_{Ni}=230$ ppm.

In Fig. 2 we have also represented the ratio Ag/Au versus Cu/Au, for some items from the reference 7., items which are analysed also in the present work: the 3 idols Moigrad Neolithic (samples A1, A2 and A3). Our results are in a relative good agreement with the results of reference 7. The samples from Argeş hoard, beads and rings present a wide range of concentrations as concerning Cu, but also they can be marked on the graph like a relatively separate region.

In Fig. 3 Sb - Zn correlation is shown for some samples. The samples from Argeş hoard form a relatively close cluster. For the beads $\bar{C}_{Zn}=328\pm61$ ppm, and $\bar{C}_{Sb}=14\pm5$ ppm and for the rings $\bar{C}_{Zn}=190\pm86$ ppm, and $\bar{C}_{Sb}=24\pm8$ ppm

From the elements revealed in ancient gold samples, the elements Fe, Co and Ni compose a relatively aleatory background, traces of these elements can be added or removed during the manufacturing or refining process.

One can observe the presence of Fe in the gold items from Turnu Magurele.

The importance of noble metals in the gold sample is well known^{8,9}. The noble metals remain in unchanged concentrations during the processing or refining. In our samples, Ir and Os have been determined in very low concentrations. From the analysed objects we could remark some items with higher concentrations of Ir: bracelet Someşeni, sample A35: $C_{Ir}=1320\pm90$ ppb and bracelet with muff, sample A36: $C_{Ir}=520\pm40$ ppb.

In this report it was shown that RNAA can be used as a method for the study of elemental composition of ancient gold objects. By this method a number of elements like: Ir, Os, Sb, Zn, Co, Fe and Ni can be determined in the ancient gold which improves the knowledge of historians concerning these valuable objects.

References

1. Z. Goffer, 1980, Archaeological Chemistry, N.Y., J. Wiley & Sons, 1980
2. V. M. Emeleus, Archaeometry, vol. **1** (1958) 6
3. E. R. Caley, Analysis of Ancient Metals, Oxford, Pergamon Press, 1964
4. T. Takeuchi, Radioisotopes **29** (1980) 119
5. F. Widemann, 1980, J. Radioanal. Chem. Vol. **55** (1980) 272
6. E. Pernicka, Nucl. Instr. and Methods **B 14** (1986) 24
7. A. Hartmann, Prehistorische Goldfunde aus Europa II, Mann. Berlin, 1982
8. N. D. Meeks and M. S. Tite, Journal of Archaeological Science, **7** (1980) 267
9. V. Cojocaru, 3rd General Conf. of the Balkan Phys. Union, Sep. 1997, Cluj, Romania, Abstracts, p.495

FIGURE CAPTIONS

Table 1: Table 1 List of ancient gold objects analysed in this work

Sample	Ancient gold object, hoard, provenance, dating, inventory number
A1	"Violin"- Idol, Moigrad, jud. Sălaj, 3 rd millenium, B.C., inv.no. 54570
A2	Masc. Idol Moigrad, 3 rd millenium, B.C., inv.no. 54571
A3	Femin. Idol Moigrad, 3 rd millenium, B.C., inv.no. 54572
A4	Bracelet, Lungoci, jud. Galați, inv.no. 89336
A5	Disk Phalera, Ostrovul Mare, jud. Mehedinti, 15 th century B.C., inv.no. C456
A6	Disk Phalera, Ostrovul Mare, inv.no. C 473
A10	Ring "spiral", Argeș, 15 th - 14 th centuries B.C., inv.no. C 429
B3-B9	Beads, Argeș
B10-B19	Rings "spiral", Argeș
A11	Muff, Turnu Măgurele, jud. Teleorman, 13 th -12 th centuries B.C., inv.no. 11039
A12	Muff, Turnu Măgurele, inv.no. 11042
A14	Muff, Turnu Măgurele, inv.no. 11040
A15	Muff, Turnu Măgurele, inv.no. 11043
A16	Ring "spiral", Turnu Măgurele, inv.no. 92037
A17	Tubular Object, Turnu Măgurele, inv.no. 11038
A18	Bracelet, Dipșa, jud. Bistrița-Năsăud, 13 th-12 th centuries B.C., P 23484
A19	Diadem, Bunești-Averești, jud. Vaslui, 3 rd century B.C.
A20	Ingot, Feldioara, , jud. Brașov, 379-380 A.D.

- A21 Diadem, Balaci, jud. Teleorman, 5 th century A.D.
- A22 Bracelet, Balaci, inv.no. 9133
- A23 Bracelet, Balaci, inv.no. 9134
- A24 Buckle Moigrad, 5 th century, jud. Sălaj, inv.no. 54587
- A25 Bracelet Moigrad, 5 th century, inv.no. 54585,
- A26 Bracelet Moigrad, 5 th century, inv.no. 54584
- A27 Bracelet Moigrad, 5 th century, inv.no. 54586
- A28 Ear, Moigrad, 5 th century, inv.no. 54588
- A29 Floral applique, Buzău, 5 th century, inv.no. 9014
- A30 Buckle Buzău, inv.no. 11060
- A31 Ear ring pendant, Buzău
- A32 Tubular object, Mangalia, 4 th century, inv.no. 8977
- A33 Mangalia, fragment necklace, inv.no. 8976
- A34 Piece, Mangalia, inv 8975
- A35 Bracelet, Someșeni, Cluj, inv.no. 54252
- A36 Bracelet with Muff, inv.no. 11084
- A38 Bowl "with snails", Dobrogea, inv.no. 11091

Table 2: Concentration of elements in different ancient gold objects, by RNAA, (Cu by INAA)

Sample	Ag	Cu	Ir	Os	Sb	Zn	Fe	Co	Ni
	%	%	ppb	ppm	ppm	ppm	ppm	ppm	ppm
A1	4.98	0.523	24	<1	1.3	7.1	190	1.2	128
A2	6.01	0.404	8.8	<3	3.1	29	1420	0.8	138
A3	6.03	0.323	<10	<4	1.5	38	<2000	4.26	<300
A4	7.65	0.554	125	<8	5.2	9.8	-	0.67	1050
A5	21.8	0.303	-	-	-	42	-	0.26	-
A6	17.6	0.794	-	-	-	29	-	-	-
A7	21.6	0.351	11	23	24	40	760	-	-
A8	20	0.408	67	<20	<1	15	-	0.015	-
A9	11.6	0.315	3	-	0.94	14	-	0.93	-
A10	20	0.554	-	-	1.9	12	-	0.12	-
B3	24.7	1.03	-	-	12.3	430	-	-	-
B4	30.5	0.725	-	-	8.4	309	3980	-	-
B5	27.3	0.625	324	34	22	490	6025	-	-
B6	11.2	58.7	-	25	3.8	125	1890	-	-
B7	23.6	15.5	-	17	7.7	118	2280	-	230
B8	26.5	3.71	30	30	20	309	5374	-	-
B9	30.3	0.998	-	114	23	518	5220	-	-
B10	17.9	0.554	-	242	78	258	5111	-	-
B11	14.7	46.1	-	7	8	76	1290	-	-
B12	24.4	11.1	-	-	3	195	1104	-	-
B13	27.5	2.75	-	24	24	152	1846	-	-
B14	20.6	0.610	15	8.7	6.1	142	1364	-	-
B15	13.3	45.1	-	-	5.2	15	-	-	-
B17	18.5	38.4	-	-	32	762	-	-	-
B18	33.6	0.399	-	-	16.5	54	-	-	-
B19	30.0	0.289	-	-	46	53	-	-	-

Sample	Ag	Cu	Ir	Os	Sb	Zn	Fe	Co	Ni
A11	51.6	2.14	15	-	-	11	-	0.94	-
A12	17.1	0.571	91	-	5.7	30	-	-	-
A14	11.1	2.49	198	-	7.5	12	-	-	-
A15	15.9	0.285	36	-	0.7	1.7	-	-	-
A16	21.2	2.63	-	-	-	-	-	-	-
A17	16.0	0.9340	-	-	-	2.56	-	-	-
A18	10.7	0.337	98	-	-	62	-	0.98	-
A19	0.7702	0.6020	20.3	-	-	0	-	-	-
A20	0.74	-	140	-	-	0	-	-	-
A21	12.7	1.84	145	-	-	30	-	1.8	-
A22	8.09	0.389	-	-	-	23	-	0.94	-
A23	10.8	-	35	-	-	44	-	-	-
A24	8.32	6.89	455	11	-	3400	-	0.078	230
A25	9.44	0.4147	-	-	1	16	-	0.676	-
A26	6.42	0.522	-	-	7.2	14	-	1.1	-
A27	7.21	0.729	-	-	2.2	15	-	0.738	-
A28	5.62	0.314	149	-	1	54	-	4.47	420
A29	11.5	4.000	72	-	3.6	615	-	0.89	-
A30	3.05	0.486	250	-	2.4	230	-	-	-
A31	8.24	5.14	44	-	0.18	19	-	-	-
A32	10.6	4.06	420	-	2.2	27.3	-	2.4	-
A33	2.92	6.26	587	-	2.1	24.7	-	1.5	250
A34	3.71	0.242	488	-	8.6	35	-	2.3	-
A35	4.74	0.646	1320	-	11.7	61	-	2.6	-
A36	5.75	3.13	520	-	12.6	45	-	1.1	-
A38	13.44	8.62	403	-	44	70	-	0.9	-

- = under the detection limit

Fig. 1 Diagram of the radiochemical separation procedure

Fig. 2 Ratio Ag/Au versus the ratio Cu/Au for different ancient gold items, by INAA

Fig. 3 Concentration of Sb versus the concentration of Zn for different ancient gold objects, by RNAA

TABLE CAPTIONS

Table 1 List of analysed samples.

Table 2 Concentration of elements in different ancient gold objects, by RNAA. The concentrations are expressed in % (Ag and Cu), in ppb (Ir) and in ppm (Os, Sb, Zn, Fe, Co and Ni)

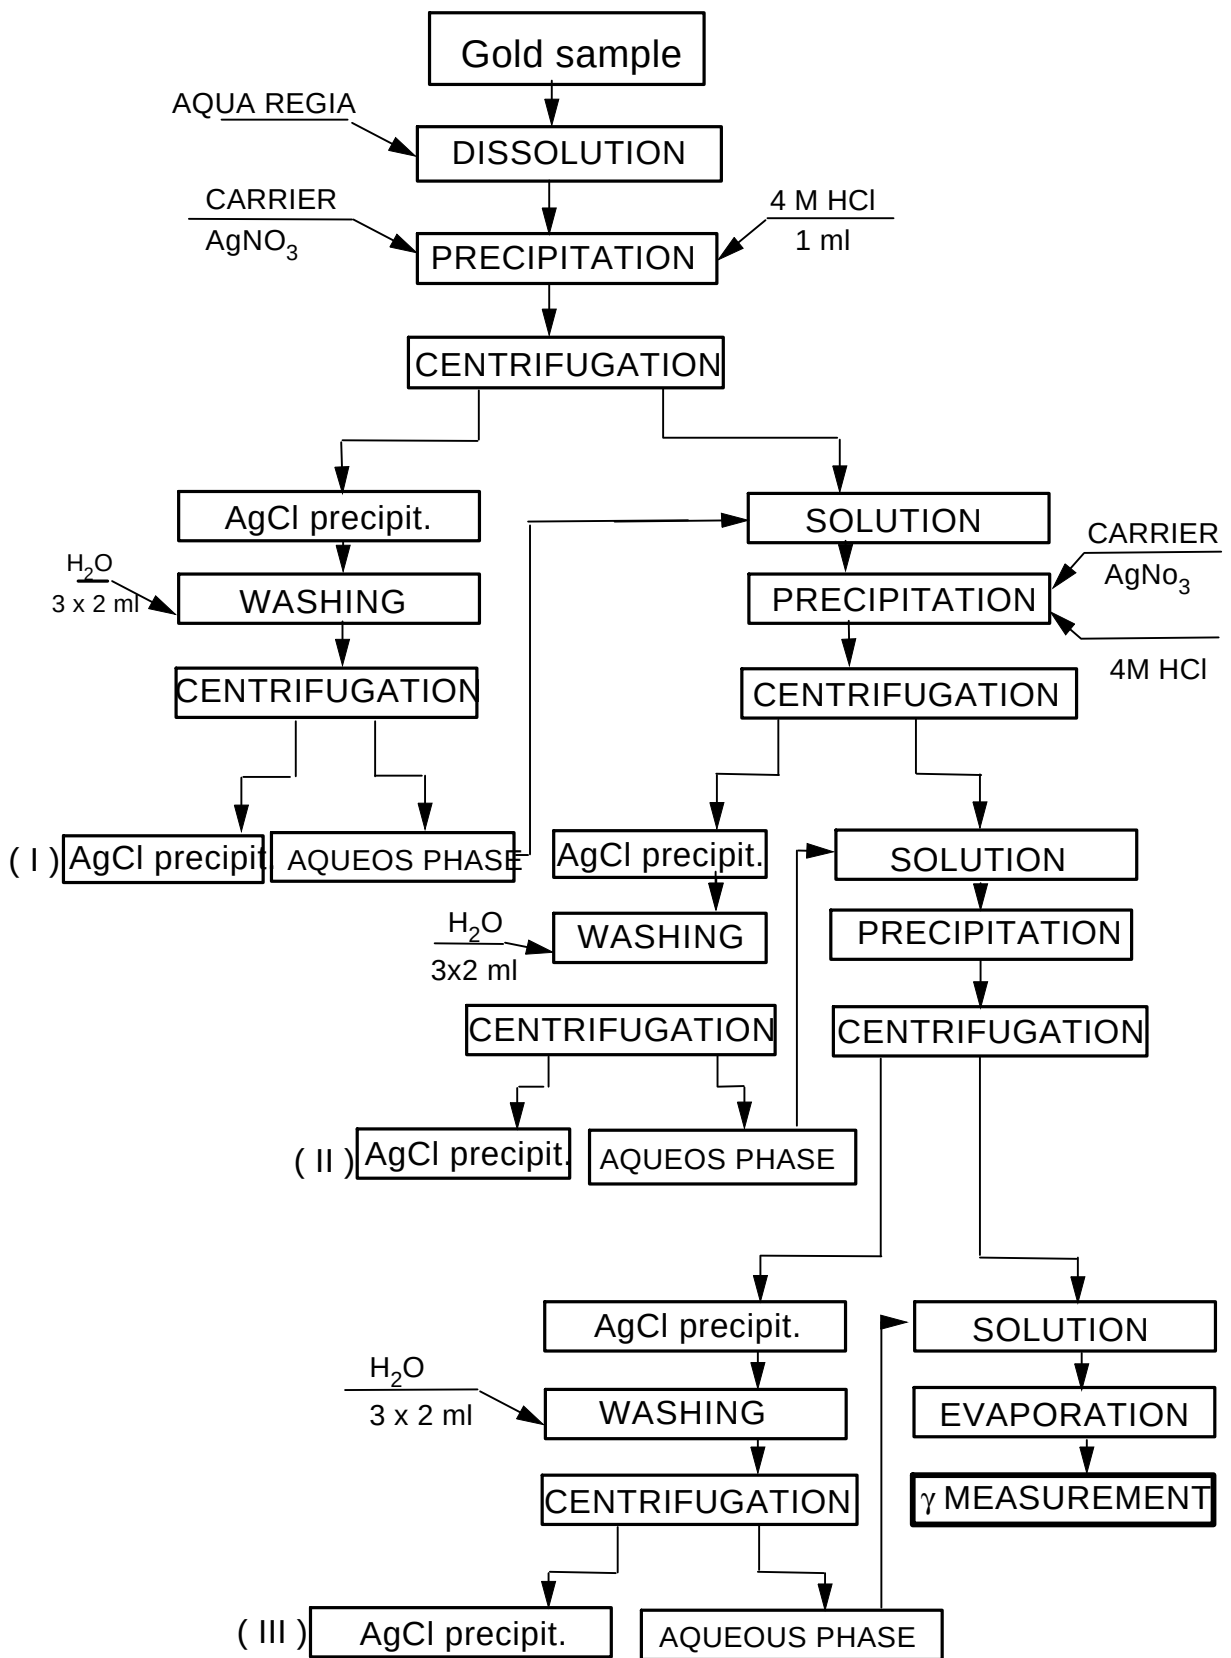


Fig. 1

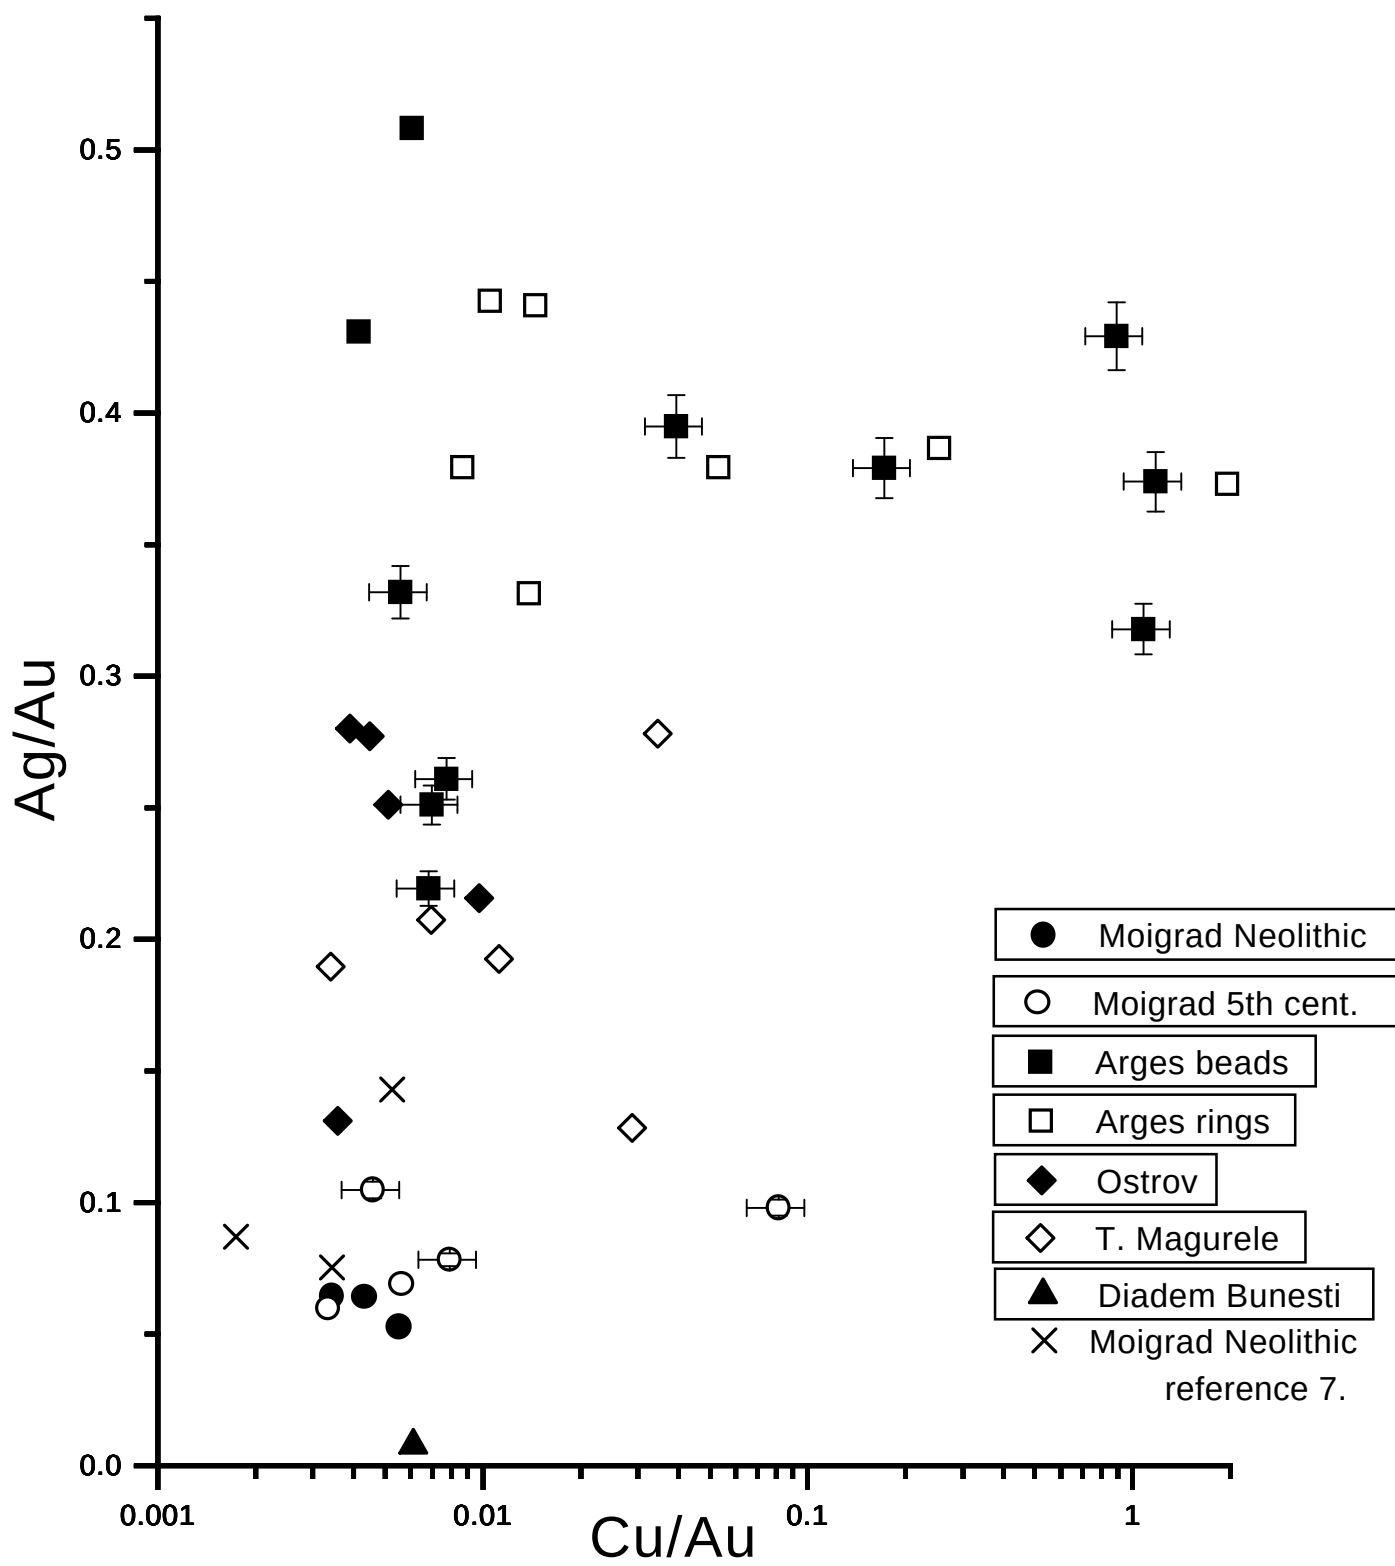


Fig. 2

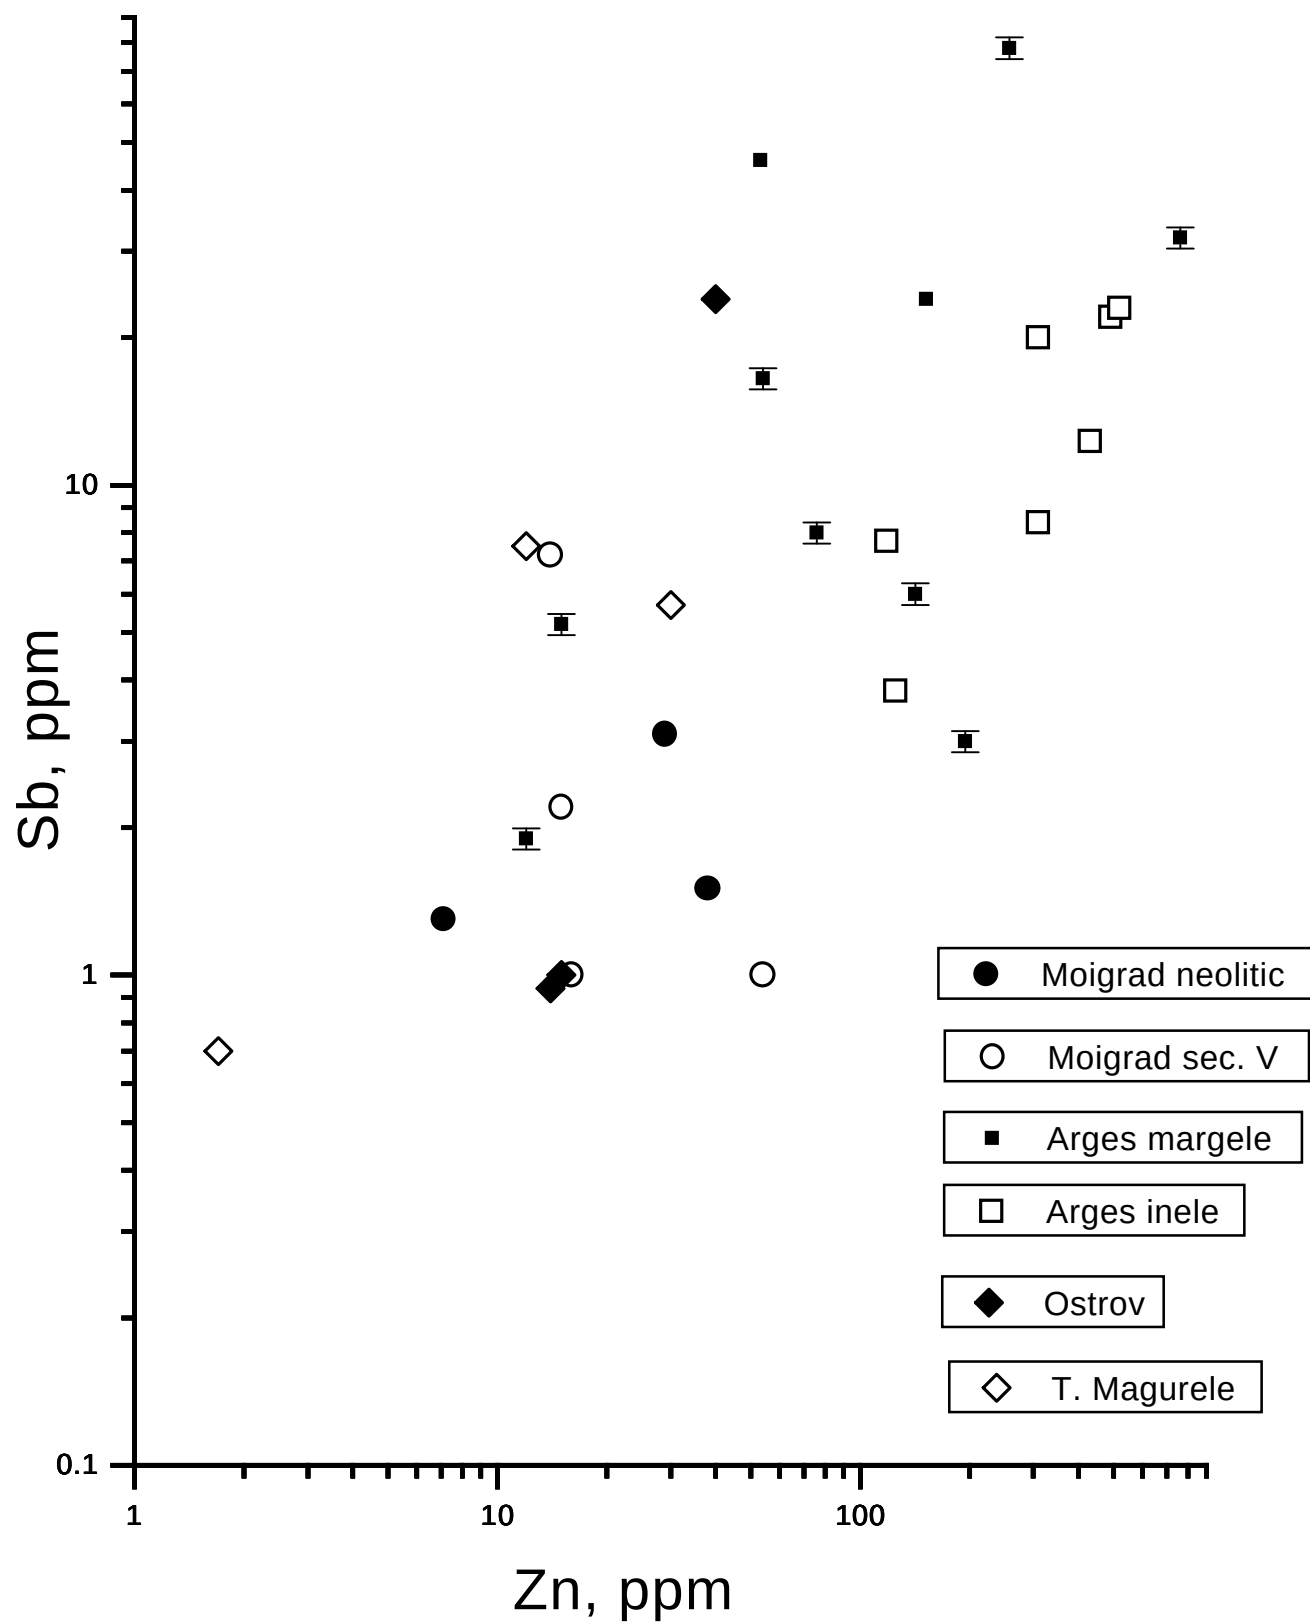


Fig. 3